

STRENGTH LOSS CHARACTERISTICS OF FLY ASH BASED GEOPOLYMER CONCRETE SUBJECT TO HIGHER TEMPERATURES

Benny Joseph^{a*}, George Mathew^b

^aDepartment of Civil Engineering, V K C E T Thiruvananthapuram74, Kerala State, India

^bDivision of Safety and Fire Engineering, School of Engineering, Cochin University of Science and Technology, Cochin-22, Kerala State, India.

* Corresponding author

doi: <https://doi.org/10.21467/proceedings.179.32>

ABSTRACT

Fly ash based geopolymer concrete, one of the environment friendly alternatives to conventional concrete, is expected to behave better at elevated temperatures. However limited information is available about its behaviour at elevated temperatures. This paper presents the engineering properties of fly ash based geopolymer concrete after exposure to elevated temperatures and compares the corresponding results with those of a conventional concrete having almost the same compressive strength of geopolymer concrete (at ambient temperature). The specimens were heated at a constant rate (5.5 °C /minute) to different set temperatures (200,400, 600 and 800 °C). They were cooled to ambient temperature by air cooling and water cooling and then tested for their strength properties. It could be observed that, the fly ash based geopolymer concrete undergoes a higher rate of strength loss during its early heating period (up to 200 °C) compared to OPC concrete. However, the residual strength properties of both the concrete are almost the same at 400 °C temperature exposure and beyond 600 °C, while OPC concrete loses its strength properties rapidly; geopolymer concrete improves its strength. Hence, it could be concluded that the fly ash based geopolymer concrete could be considered as a better sustainable material than conventional concrete under the situations where it may be exposed to temperatures beyond 400 °C.

Keywords: Geopolymer, Fly ash, Concrete, High temperature, Engineering properties

1. Introduction

Construction industry requires materials and technologies that are sustainable and friendly to environment. Cement is the most widely used construction material. Its manufacturing process results in emission of greenhouse gas [1]. Fly ash, a waste product generated from thermal power stations results in environmental issues, if not disposed off properly [2]. Use of fly ash based geopolymer concrete in construction will not only eliminate consumption of cement but also utilize industrial waste effectively. Geopolymer (GP) concrete is emerging as one of the environment friendly alternatives to Ordinary Portland Cement (OPC) concrete. In GP concrete, a geopolymer binder is formed by alkali activation of amorphous alumina-silicate material under warm atmosphere. The result of geopolymerisation is the formation of a three dimensional structural framework which is formed after dissolution, hydrolysis and polycondensation reaction [3,4]. The effectiveness in the geopolymerisation process depends on type, particle size, and the degree of amorphous character and the chemical composition of alumino-silicate source materials [5-8]. Variables such as water to solid ratio, type and concentration of alkali, temperature of curing, period of curing etc. influence the properties of geopolymer mortar and concrete [9-11].



© 2025 Copyright held by the author(s). Published by AIJR Publisher in "Proceedings of the Second International Conference in Civil Engineering for a Sustainable Planet: ICCESP 2024". Organized on 6-8 December 2024, by Habilete Learning Solutions, Kollam, Kerala, India in collaboration with. Marian Engineering College, Trivandrum, Kerala; American Society of Civil Engineers (ASCE); and ASCE India Section southern Region.

Proceedings DOI: [10.21467/proceedings.179](https://doi.org/10.21467/proceedings.179); Series: AIJR Proceedings; ISSN: 2582-3922; ISBN: 978-81-984081-7-4

For normal applications, OPC concrete generally provides satisfactory thermal resistance upto a temperature exposure of about 400 °C. However, beyond this temperature, its strength properties decreases rapidly and wide spread cracking and subsequent spalling occurs [12-17]. Because of the low energy need for the production and expected better behaviour at elevated temperatures compared to OPC concrete, geopolymer compounds are being considered as sustainable fireproof building materials, heat insulators etc. However, most of the studies at elevated temperatures are on geopolymer paste and mortar [18-19]. Kong and Sanjayan [20], based on their study on fly ash based geopolymer concrete, have reported that the compressive strength of geopolymer concrete when exposed to elevated temperatures are influenced by the specimen size, size of coarse aggregate and type of aggregate. Kong et al. [19] observed a higher strength loss at elevated temperatures for metakaolin based geopolymer paste as against fly ash based geopolymer paste. At 800 °C, while metakaolin based geopolymer paste continued its strength loss, they observed a strength gain in fly ash based geopolymer. Review of literature shows that, a systematic study on the engineering properties of geopolymer concrete exposed to elevated temperatures is still a gap area. Present paper focuses on an experimental investigation on the engineering properties of geopolymer concrete exposed to elevated temperatures and compares the corresponding behavior of a comparable OPC concrete.

2. Experimental program

Fly ash based geopolymer (GP) concrete specimens were made and were exposed to a constant rate of temperature increase (5.5 °C/ minutes). The specimens were then cooled to ambient temperature by air cooling and water cooling. Specimens were then tested at ambient temperature to determine their various engineering properties. OPC concrete was designed in such a way that the cube compressive strength of both GP and OPC concrete are almost the same at ambient temperature so that their test result could be compared.

2.1. Materials

Low calcium fly ash (ASTM Class F) obtained from a thermal power station (India) has been used for the present study. The chemical composition of fly ash is presented in Table 1. The fly ash used had a specific gravity of 1.9. Partilce size distribution and XRD analysis are available in a publication [21].

Table 1 Chemical composition of fly ash

Parameter	Content% by mass)
SiO ₂	59.70
Al ₂ O ₃	28.36
Fe ₂ O ₃ +Fe ₂ O ₄	4.57
CaO	2.10
Na ₂ O	0.04
MgO	0.83
Mn ₂ O ₃	0.04
TiO ₂	1.82
SO ₃	0.40
Loss of ignition	1.06

A mixture of NaOH and Na₂SiO₃ solution (SiO₂ = 34.64%, Na₂O= 16.27%, water 49.09%) was used as alkali solution in the present investigation. NaOH pellets of 98% purity were used to make sodium hydroxide solution. The specific gravity of alkali liquid solution, having Na₂SiO₃/NaOH (molarity 10) ratio 2.5 was 1.54.

Crushed granite aggregates of nominal size 20 mm was used as coarse aggregate. Natural river sand having fineness modulus of 2.36 was used as fine aggregate. The specific gravity of coarse and fine aggregate was 2.72 and 2.64 respectively. Ordinary Portland cement was used for making OPC concrete.

2.2 Mix proportioning

A preliminary study was carried out to arrive at the optimum proportion of the various constituents of GP concrete and details are presented elsewhere [22]. Accordingly, the parameters that kept constant in this investigation includes, aggregate content by volume (70%), ratio of fine aggregate to total aggregate(0.35), ratio of alkali to fly ash by mass (0.55), molarity of NaOH (10), ratio of Na₂SiO₃ to NaOH (2.5), ratio of water to geopolymer solid (0.25). The quantity of materials required to produce 1m³of GP concrete based on the above proportions is given in Table 2.

Table 2 Quantity of materials required to produce 1m³of GP and OPC concrete

Mix ID	Cemen (kg)	Flyash (kg)	Coarse aggregate (kg)	Fine agregate (kg)	NaOH solution (kg)	Na ₂ SO ₃ (kg)	Super plasticizer (kg)
GP concrete	----	310	1204	648	48.7	121.7	6.2
OPC concrete	475	-----	1204	648	-----	-----	1.9

2.3. Mixing

The prepared NaOH solution was first mixed with calculated amount of Na₂SiO₃ liquid and kept for 24 hours before use. Coarse and fine aggregates in saturated surface dry conditions were thoroughly mixed with fly ash in a pan mixture. The alkali liquid and Naphthalene based superplasticizer (2% by weight of fly ash) were mixed together and then added to the dry mix. The whole mixture was then mixed together for 5 minutes.

2.4. Casting of specimens

Steel moulds of size 150 mm x 150 mm x 150 mm, 100 mm x 100 mm x 500 mm, and 150 mm diameter, 300mm height were used for mechanical properties of both GP and OPC concrete. The fresh GP and OPC concrete filled in 3 layers and compacted with the help of a table vibrator. The OPC concrete specimens were kept in the mould for 24 hours under laboratory conditions and then they were demoulded and immersed in water for curing. GP concrete specimens were kept under laboratory condition for 60 minutes and then, after covering with thin steel plate, they were subjected to heat curing in an electric oven at 100 °C for a period of 24 hours. The curing temperature and period of curing were arrived at based on a preliminary study [22]. After temperature curing, GP concrete specimens were kept at room temperature till they were tested. Geopolymer paste was prepared with the same GP concrete and specimens were prepared for different microstructural analysis.

2.5. Heating and testing of specimens

OPC concrete specimens were taken out of curing tank on the 27th day, their surfaces dried with cloth and kept in the laboratory for 24 hours. The specimens were then kept in an oven for 1 hour at 60 °C to remove surface moisture so that exposure spalling could be avoided during heating.

GP and OPC concrete specimens were heated in an electric furnace to 200 °C , 400 °C , 600 °C and 800 °C . The rate of heating was kept at 5.5 °C /minute. After attaining the target temperature, specimens were kept at the same temperature for 1 hour to ensure that the specimens attain a uniform temperature throughout. The heated specimens were then cooled by two different methods namely air cooling and water cooling. Both GP and OPC concrete specimens were tested after they were cooled down to ambient temperature.

3.1 Compressive strength

Table 3 gives the compressive strength of GP and OPC concrete after exposed to elevated temperature. From the Table 3, it could be observed that, for almost the same compressive strengths of both GP and OPC specimens at ambient temperature, there is a higher strength loss for GP concrete during the early stages of the temperature rise. In the present study, at 200 °C , while air cooled and water cooled OPC concrete had a strength loss of about 0.4 % and 9% respectively, the corresponding loss of strength of GP concrete is about 26 % and 31% respectively.

Table 3 Cube compressive strength of GP and OPC specimens after exposed to elevated temperatures

Exposure Temperature (°C)	GP Concrete				OPC Concrete			
	Air cooled		Water cooled		Air cooled		Water cooled	
	Comp. strength (MPa)	SD*						
Ambient (28)	57.30	0.45	-	-	59.85	0.68	-	-
200	42.52	0.68	39.40	0.68	59.60	1.17	54.37	0.88
400	37.33	0.45	35.85	0.44	42.66	0.44	39.85	1.14
600	30.82	0.67	28.00	0.94	32.44	0.84	31.48	0.54
800	32.88	0.38	31.30	0.31	21.00	0.31	19.55	0.62

* - SD - Standard deviation

The FTIR spectrum analysis of GP paste exposed to elevated temperatures is presented in figure 1 [23], which shows a shift in the wave number and a substantial reduction of the peak in Si-O-Al (aluminosilicate) and Si-O-Si regions (wave number 460cm⁻¹ to 1088cm⁻¹) at a temperature exposure of 200 °C, indicating a reduction in their bonding force and decrease in chain length [6]. Also, the bands representing water molecule (hydroxyl groups) in GP paste showed a marked decrease in their peak at a temperature exposure of 200 °C and further increase in exposure temperature did not cause any further decrease in these peaks (wave number 3440 cm⁻¹). This means that, most of the weakly bound water molecules that were either adsorbed on the surface or trapped in the large cavities between the geopolymeric products get expelled at about 200 °C. The combined result of the above may lead to a higher strength reduction in GP concrete compared to OPC concrete during the initial heating process.

Even though the free water in concrete gets removed during the initial heating of OPC, the strength gained due to the hydration of unreacted cement particles compensates the strength loss due to other parameters in concrete when heated up to about 200 °C; a behaviour well accepted by many researchers [13,24].

Figure 2 shows the residual compressive strength of test specimen (in percentage of strength at ambient temperature) after the exposure to different temperatures and tested after cooling by air and water cooling methods. From Fig 2, it could be observed that, the air cooled OPC specimen does not experience much

strength reduction up to 200 °C and beyond this, there is more or less a constant rate of strength reduction upto 800 °C .

Compared to air cooled OPC specimen, the rate of strength reduction between 200 °C and 400 °C is less for GP concrete and the percentage residual strength is almost same for both the types of concrete at 400 °C. It may further be noted that, while the rate of strength loss between 400 °C and 600 °C is almost the same for both the types of concrete. However GP concrete shows a strength gain beyond 600 °C, while OPC concrete continues to lose its strength.

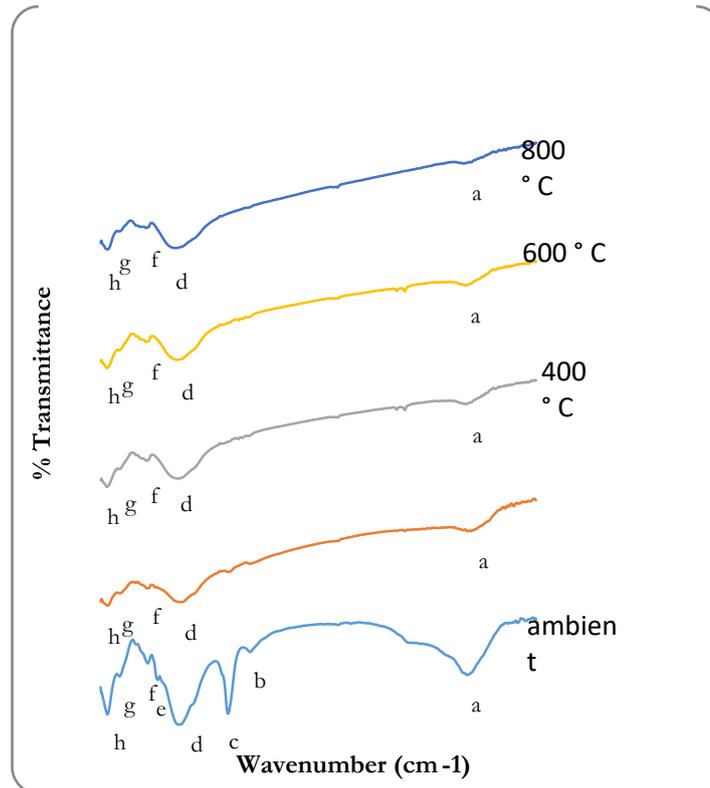


Figure 1 FTIR of Geopolymer paste exposed at different temperature (air cooled)

ambient : $a=3430\text{ cm}^{-1}$, $b=1635\text{ cm}^{-1}$, $c=1453.13\text{ cm}^{-1}$, $d=1045\text{ cm}^{-1}$, $e=870.26\text{ cm}^{-1}$ $f=788\text{ cm}^{-1}$, $g=555\text{ cm}^{-1}$ and $h=455\text{ cm}^{-1}$

200 °C: $a_1=3436\text{ cm}^{-1}$ $d_1=1062\text{ cm}^{-1}$ $f_1=795\text{ cm}^{-1}$ $h_1=458\text{ cm}^{-1}$

400 °C: $a_2=3399\text{ cm}^{-1}$ $d_2=1046\text{ cm}^{-1}$ $f_2=788\text{ cm}^{-1}$ $h_2=446\text{ cm}^{-1}$

600 °C : $a_3=3419\text{ cm}^{-1}$ $d_3=1039\text{ cm}^{-1}$ $f_3=776\text{ cm}^{-1}$ $h_3=451\text{ cm}^{-1}$

800 °C: $a_4=3399\text{ cm}^{-1}$ $d_4=1006\text{ cm}^{-1}$ $f_4=775\text{ cm}^{-1}$ $h_4=453\text{ cm}^{-1}$

From the XRD analysis (figure 3) of GP paste[23], an additional polymerization of GP concrete could be observed for a temperature exposure after 600 °C, which is evident from the increased glass phase content above 600 °C, as against the 90 % glass phase content up to 600 °C. Also, while the FTIR spectrum of GP paste showed only marginal reduction in the peak intensities over the Si-O-Al and Si-O-Si region for the temperature exposure between 200 °C and 600 °C, the peak intensity corresponding to Si-O-Si linkage

Further, the reason for a lower compressive strength of water cooled OPC specimen compared to air cooled specimen is the micro cracks developed subsequent to the induced thermal shock [17,21]. The free calcium hydroxide present in hydrated Portland cement decomposes into calcium oxide at high temperature. If this calcium oxide is wetted after being cooled, it transforms into calcium hydroxide again, causing a volume change (may be up to about 40%) and this may also result to the formation of micro cracks in concrete

3.2. Tensile strength

Tables 4 and 5 shows the split tensile strength and flexural strength of GP and OPC specimen respectively, tested after exposure to elevated temperatures. The plots of these residual strengths in terms of percentage initial strength are given in the fig 5 and 6 respectively. From Tables 4 and 5 as well as from figs.4 and 5, it could be observed that, both split and tensile strength of GP concrete is slightly lower than the corresponding values of OPC concrete upto a temperature of 400 °C . Beyond this temperature, GP concrete behaves better. Further, similar to the compressive strength, beyond 600 °C, there is a strength gain for GP concrete in both split and flexural strength. Similar behaviour has been observed by other investigators [29]. In this investigation, the residual split tensile strength of aircooled GP concrete exposed to 600 °C is 32.3% and that in OPC concrete is 27.0% . However, the corresponding values at 800 °C exposure temperature are respectively 35.6% and 19.3%. Further, the rate of strength reduction of both OPC and GP concrete is more or less the same upto 600 °C in the case of split tensile strength as well as flexural strength.

Table 4 Split tensile strength of GP and OPC specimens after exposed to elevated temperatures

Exposure Temperature (°C)	Exposure	GP Concrete		OPC Concrete									
		Air cooled	Water cooled	Air cooled	Water cooled								
		Split tensile strength (MPa)	Split tensile strength D* (MPa)	Split tensile strength (MPa)	Split tensile strength D* (MPa)								
Ambient (27)	5.44	0.76	5.47	0.46	200	4.17	0.38	3.89	0.49	4.45	0.63	4.30	0.92
400	2.61	0.89	2.47	0.69	3.04	0.87	2.89	0.43					
600	1.76	0.86	1.37	0.55	1.48	0.64	1.45	0.78					
800	1.94	0.75	1.58	0.69	1.06	0.57	0.95	1.10					

* SD - Standard deviation

Table 5 Flexural strength of GP and OPC specimens after exposed to elevated temperatures

Exposure Temperature (°C)	Exposure	GP Concrete		OPC Concrete				
		Air cooled	Water cooled	Air cooled	Water cooled			
		Flexural strength (MPa)	Flexural strength SD* (MPa)	Flexural strength (MPa)	Flexural strength SD* (MPa)			
Ambient (28)	5.30	0.68			5.44	0.45		
200	4.23	0.53	4.10	0.68	4.53	0.67	4.40	0.38
400	2.89	1.21	2.61	0.86	3.36	0.77	3.19	0.82
600	1.86	0.87	1.52	0.58	1.72	0.83	1.49	0.89
800	1.90	0.47	1.65	0.96	0.72	0.66	0.61	0.87

* SD - Standard deviation

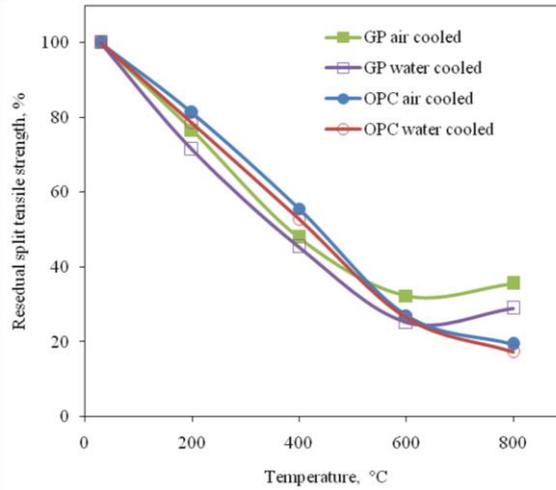


Figure 4 Residual split tensile strength of GP and OPC concrete after exposure to elevated temperatures

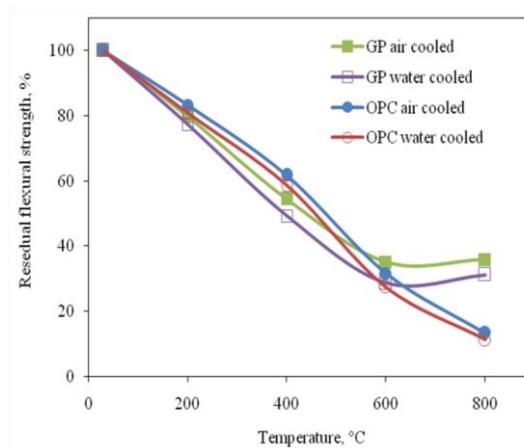


Figure5 Residual flexural strength of GP and OPC concrete after exposure to elevated temperatures

3.3. Modulus of elasticity

The slope of secant drawn at one third of the characteristic compressive strength of concrete has been considered as the modulus of elasticity of concrete. Standard cylinder specimens have been used to determine the modulus of elasticity.

Figure 6 shows the variation of the modulus of elasticity (%) of GP and OPC concrete after exposure to elevated temperatures. From fig, it could be observed that, compared to OPC concrete, while GP concrete shows a lower residual modulus of elasticity upto about 450 °C, and higher values for exposure temperatures above 450 °C. Also, unlike OPC concrete, GP concrete does not undergo further reduction in modulus of elasticity beyond 600 °C, a behavior similar to that of compressive strength of GP concrete. For the present study, at 600°Cair cooled GP had a residual modulus of elasticity of 23.2% as against 9.2 % in the case of OPC concrete. Further, at 800 °C, air cooled GP concrete had a residual modulus of elasticity of 24.5% and the corresponding value of air cooled OPC concrete is only 2.9%.

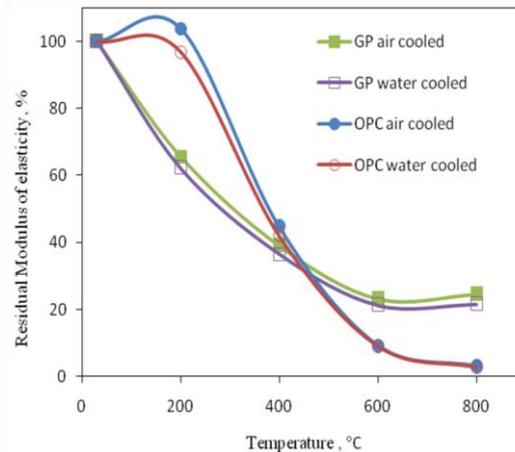


Figure6 Modulus of elasticity of GP and OPC concrete after exposure to elevated temperatures

4. Conclusions

Conclusions derived from the study conducted on the fly ash based concrete are as follows. FA based geopolymer (GP) concrete undergoes a high rate of strength loss (compressive strength, tensile strength and modulus of elasticity) during its early heating period (up to 200 °C) compared to OPC concrete. The high rate of strength loss in GP concrete at its early heating period is contributed primarily due to the chemical restructuring of Si-O-Al (alumino silicate) and Si-O-Si compound and due to the formation of micro crack as a result of the removal of water (weakly bound and free water) from the geopolymer matrix. At exposure beyond 600 °C, the unreacted crystalline materials in GP concrete get transformed into amorphous state and undergo polymerization. There is no further strength loss (compressive strength, tensile strength and modulus of elasticity) in GP concrete, whereas, OPC concrete continues to lose its strength properties at a faster rate beyond a temperature exposure of 600 °C. In the present study, beyond 600 °C, both air cooled GP and OPC concrete had about 54% residual cube compressive strength (compared to the strength at ambient temperature, which is almost the same for both GP and OPC concrete). However, at 800 °C, while GP concrete slightly gained its residual strength (to 57%), while OPC concrete continued to lose its strength (35% residual strength). □ Effect of thermal shock due to water cooling on GP and OPC concrete after exposed to elevated temperatures is similar. For the present study, both GP and OPC concrete had a maximum strength loss of about 10% due to water cooling. Hence, it could be concluded that the fly ash based geopolymer concrete could be considered as a better sustainable material than conventional concrete under the situations where it may be exposed to temperatures beyond 400 °C.

Conflict-Of-Interest Statement

This article does not present any conflict of interest regarding the study carried out, as it is our own work, and publication of results.

References

- [1] V .M. Malhotra, Making Concrete ‘Greener’ With Fly Ash, ACI Concr. Int. 21 (1999) 61-66.
- [2] B.Lokeshappa, Dikshit AK, Disposal and Management of Flyash, International Conference on Life Science and Technology. IPCBEE 3(2011) 11-14
- [3] J.G.S Van Jaarsveld , J.S.J. Van Deventer, L. Lorenzen , The potential use of Geopolymeric materials to immobilise toxic metals: Part I. Theory and applications, Mineral Engineering. 10(1997) 659-669.
- [4] J. Davidovitz, Chemistry of geopolymer system-Terminology, Geopolymer International Conference, France(1999).

- [5] E.I. Diaz , E.N. Allouche, S. Eklund , Factors affecting the suitability of fly ash as source material for geopolymers, *Fuel* 89(2003) 992–996.
- [6] P.Duxson,J.L. Provis, G.C. Lukey, S.W. Mallicoat Understanding the relationship between geopolymer composition, microstructure and mechanical properties, *Colloids and surf.* 269 (2005) 47-58.
- [7] H.Xu , J.S.J.Van Deventer ,Effect of Source Materials on Geopolymerization., *Ind. Eng. Chem. Res.*42(2003) 1698-1706.
- [8] Temuujin , P.P.Williams, V.A.Riessen, Effect of mechanical activation of fly ash on the properties of geopolymer cured at ambient temperature, *J. Mater. Proc. Tech* 209(2009)5276– 5280.
- [9] R.N.Thakur ,S. Ghosh, Effect of mix composition on Compressive strength and Microstructure of FA based Geopolymer composites, *ARN J.of Eng Appl.Sc.*4(2009) 68-74
- [10] D.Hardjito,S.E. Wallah,D.M.J. Sumajouw, B.V. Rangan, On the development of fly ashbased geopolymer concrete, *ACI Mater. J.* 101(2004) 467–472.
- [11] A.M. Fernández-Jiménez,A. Palomo ,C. Lopez-Hombrados , Engineering properties of alkaliactivated fly ash concrete, *ACI Mater. J.* 103(2006) 106–112.
- [12] L. T. Phan , Fire performance of high strength Concrete: A report of the State of the Art, National Institutes of Standards and Technology, Maryland(1996).
- [13] W.M. Lin, T.D. Lin, C. L. J. Powers, Microstructures of Fire-Damaged Concrete, *ACI Mater.J.* 93(1996) 199-205.
- [14] S. Y.N. Chan, G.F. Peng, M. Anson, Fire Behavior of High-Performance Concrete Made with Silica Fume at Various Moisture Contents, *ACI Mater. J.* 96,(1999)405-409.
- [15] G. Chanvillard ,L. Aloia .) Concrete Strength Estimation at Early Ages: Modification of the Method of Equivalent Age, *ACI Mater.J.* 94(1997)520-530.
- [16] G. J. Escalante, J. H. Sharp, Effect of temperature on the hydration of the main clinker phases in portland cements: Part 1. Neat cements, *Cem. Concr. Res* 28 (1998) 1259–1274.
- [17] V. Kodur, W.Khali , Effect of Temperature on Thermal Properties of Different Types of High Strength Concrete, *J. Mater. Civ. Eng.* 23(2003) 793-801.
- [18] Z.Pan, J.G.Sanjayan, Stress-strain behavior and abrupt loss of stiffness of geopolymer at elevated temperatures, *Cem and Concr. Comp* 32(2010) 657-664.
- [19] D.L.Y. Kong, J.G. Sanjayan, K.S.Crentsil , Comparative performance of geopolymers made with metakaolin and flyash after exposure to elevated temperatures, *Cem. Concr.Res.* 37(2007) 1583-1589
- [20] D.L.Y. Kong , J.G. Sanjayan, Effect of elevated temperatures on geopolymer paste, mortar and concrete, *Cem. Concr. Res* 40(2010)334–339.
- [21] George Mathew, Benny Joseph, Flexural behaviour of geopolymer concrete beams exposed to elevated temperatures, *J Building Eng.* 15 (2018) 311 – 318.
- [22] B. Joseph , G. Mathew ,Influence of Aggregate content on the Behavior of Fly ash based Geopolymer Concrete, *Scientia Iranica*19(2012)1188-1194.
- [23] George Mathew, Benny Joseph, Microstructural analysis of fly ash based geopolymer exposed to elevated temperatures, *Bull Eng.* 10 (2017) 117-122.
- [24] G.F. Peng, S.Y.N. Chan, M. Anson, Chemical kinetics of C–S–H decomposition in hardened cement paste subjected to elevated temperatures up to 800, *Adv. in Cem. Res.*13(2001):47– 52.
- [25] G.F. Peng, S.H. Bian, Z. Q. Guo, J. Zhao, X.L. Peng, Y.C. Jiang, Effect of thermal shock due to rapid cooling on residual mechanical properties of fiber concrete exposed to high temperatures, *Constr. and Build. Mater* 22(2008) 948–955.
- [26] O. Lanre, M.Asce The influence of weather on the performance of laterized concrete, *J.Eng. and appl.Sc.* 2, (2007) 129- 135.
- [27] G. Mathew, M. Paul , Influence of Fly Ash and GGBFS in Laterised Concrete Exposed to Elevated temperatures, *J.Mater.Civ.Engg.*(2013) doi: 10.1061/ (ASCE) MT.19435533.0000830.
- [28] S.N. Shoukry , G.W. William, B. Downie, M.Y.Raid , Effect of moisture and temperature on the mechanical properties of concrete, *Constr. and Build.Mater.* 25(2011) 688-696.
- [29] Manvendra Verma , Kamal Upreti, Prashant Vats, Sandeep Singh, Prashant Singh, Experimental Analysis of Geopolymer Concrete: A Sustainable and Economic Concrete Using the Cost Estimation Model, *Advances in Materials Science and Engineering*, 2022 (2022), 1-16.